arXiv:cond-mat/0605721v1 [cond-mat.str-el] 30 May 2006

Journal of Magnetism and Magnetic Materials 0 (2008) 1–0

www.elsevier.com/locate/jmmm

Evidence for Multiple Phase Transitions in $La_{1-x}Ca_xCoO_3$

M. Kriener [a,b,*], M. Braden [b], D. Senff [b], O. Zabara [b], T. Lorenz [b]

[a] *Quantum Materials Lab, Department of Physics, Graduate School of Science, Kyoto University*
[b] *University of Cologne, Zülpicher Str. 77, 50937 Köln, Germany*

Received 12 June 2005; revised 13 June 2005; accepted 14 June 2005

Abstract

We report thermal-expansion and specific-heat data of the series $La_{1-x}Ca_xCoO_3$ for $0 \leq x \leq 0.3$. For $x = 0$ the thermal-expansion coefficient $\alpha(T)$ features a pronounced maximum around $T = 50\,K$ caused by a temperature-dependent spin-state transition from a low-spin state ($S = 0$) at low temperatures towards a higher spin state of the Co^{3+} ions. The partial substitution of the La^{3+} ions by divalent Ca^{2+} ions causes drastic changes in the macroscopic properties of $LaCoO_3$. Around $x \approx 0.125$ the large maximum in $\alpha(T)$ has completely vanished. With further increasing x three different anomalies develop.

© 2008 Elsevier B.V. All rights reserved.

PACS: 75.40; 65.70;

Keywords: specific heat; thermal expansion; spin-state transition; metal-insulator transition; double-exchange mechanism

1. Introduction

$LaCoO_3$ crystallizes in a rhombohedral symmetry ($R\bar{3}c$) and has quite unusual physical properties. At low temperatures it features a nonmagnetic and insulating ground state. With increasing temperature a paramagnetic moment develops which causes a maximum in the susceptibility around 100 K [1,2]. This is usually explained in terms of a temperature-driven spin-state transition of the Co^{3+} ions which can occur in three different spin configurations: a low-spin (LS) ($t_{2g}^6 e_g^0$, $S = 0$), an intermediate-spin (IS) ($t_{2g}^5 e_g^1$, $S = 1$), or a high-spin state (HS) ($t_{2g}^4 e_g^2$, $S = 2$). At low temperatures a LS ground state is realized. The nature of the spin state at higher temperatures is controversially discussed, e. g. [1,2,3,4,5].

The spin-state transition causes also a large additional Schottky-like contribution to the thermal expansion of $LaCoO_3$ [1]. The substitution of La^{3+} by an amount x of divalent Ca, Sr, or Ba ions influences this contribution and leads to a strong suppression of the spin-state transition. Furthermore all doping series show long-range ferromagnetic order and metallic behavior at higher doping levels $x \gtrsim 0.2$. In the case of Ca doping, ferromagnetic behavior is observed for the insulating compounds $x \leq 0.2$, too [6].

2. Thermal Expansion and Specific Heat

In Fig. 1 the temperature dependence of the linear thermal-expansion coefficient $\alpha = 1/L \cdot \partial L/\partial T$ of $La_{1-x}Ca_xCoO_3$ is shown. Fig. 1 (a) clearly reveals that the pronounced maximum in the thermal-expansion data of the undoped compound ($x = 0$) is strongly suppressed with increasing doping concentration x. Above $x \gtrsim 0.125$ this indication of the spin-state transition has completely

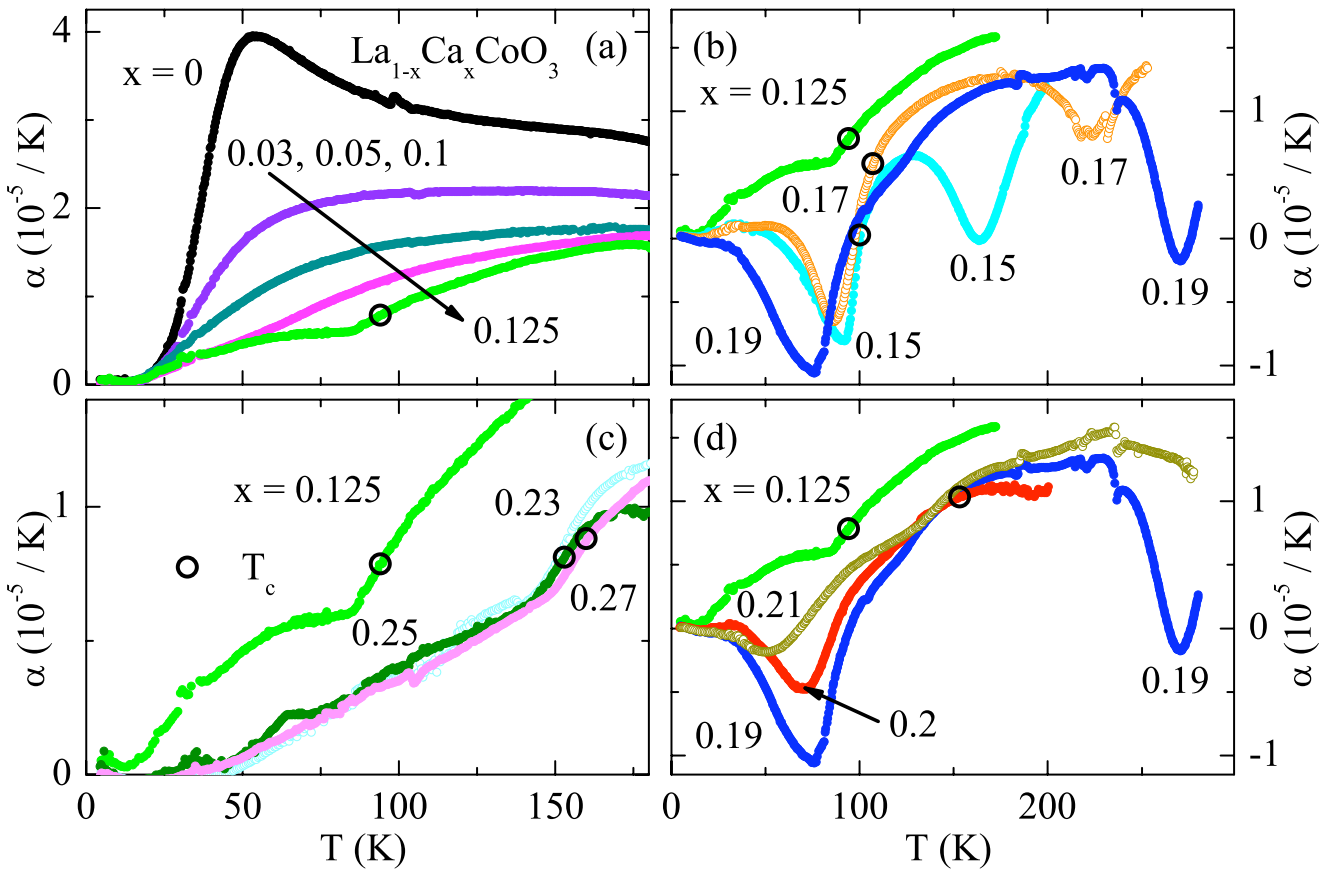

Fig. 1. Thermal expansion of $La_{1-x}Ca_xCoO_3$ for (a) $x \leq 0.125$, (b) $0.125 \leq x \leq 0.19$, (c) $0.23 \leq x \leq 0.27$ and (d) $0.19 \leq x \leq 0.21$. The curve for $x = 0.125$ is shown in each panel. The black circles denote the critical temperatures T_c of the onset of ferromagnetic order which have been taken from the magnetization data given in Ref. [6].

---

[*] Corresponding author.
Email address: `mkriener@scphys.kyoto-u.ac.jp` (M. Kriener).

0304-8853/08/$ - see frontmatter © 2008 Elsevier B.V. All rights reserved.

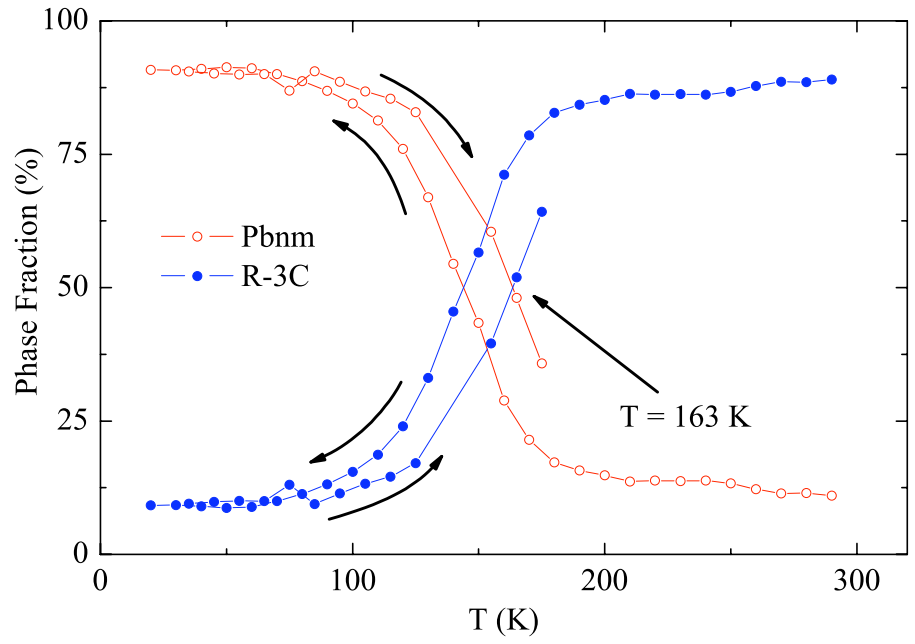

Fig. 2. Fraction of rhombohedral and orthorhombic phases as a function of T obtained from X-ray diffraction data of $La_{0.85}Ca_{0.15}CoO_3$: The arrows indicate whether the data was taken with increasing or decreasing temperature. The lines are to guide the eyes.

vanished. Instead several anomalies develop (Figs. 1 (b) – (d)): The curves for $0.15 \leq x \leq 0.21$ exhibit two distinct minima and for $x \geq 0.19$ additional kinks occur. The low-temperature minimum (LTM) shifts with increasing x to lower whereas the high-temperature minimum (HTM) moves to higher temperatures. For $x = 0.21$ we could observe only the onset of the decrease in $\alpha(T)$, because the anomaly has shifted out of the available temperature interval, i. e. $T < 300\,\mathrm{K}$, for higher doping concentrations.

At room temperature a doping induced structural phase transition from rhombohedral (R$\bar{3}$c, $x < 0.2$) to orthorhombic symmetry (Pbnm, $x \geq 0.2$) is observed [6]. This transition shifts to lower temperatures for smaller x. Fig. 2 shows the temperature dependence of the structural phase fractions for $x = 0.15$ which was obtained from X-ray diffraction data. It reveals a first-order phase transition. The HTM for $x = 0.15$ occurs at $T^{\alpha}_{min} \approx 160\,\mathrm{K}$ which coincides with the crossover from R$\bar{3}$c to Pbnm in the X-ray data. Therefore the occurrence of the HTM in $\alpha(T)$ can be attributed to a doping-induced structural phase transition. In Fig. 1, the circles (○) mark the onset of ferromagnetic order. The critical temperatures T_c of the magnetic transitions have been taken from the $M(T)$ data given in Ref. [6]. They match the occurrence of the kinks in $\alpha(T)$ for $x = 0.125$ and $x \geq 0.19$ (Figs. 1 (c), (d)). Therefore we conclude that the "kink anomalies" in the thermal-expansion data result from the onset of long-range ferromagnetic order.

In Fig. 3 specific-heat data c_p/T of $La_{1-x}Ca_xCoO_3$ is presented. One can identify several anomalies, too, although they are much less pronounced than in $\alpha(T)$. The temperatures of the minima in $\alpha(T)$ (LTM: $\star$, HTM: $\diamond$) and the onset of ferromagnetic order (○) are denoted. Fig. 3 (b) gives an expanded view for $0.15 \leq x \leq 0.2$. Please note, that for clarity the different data sets for $x > 0$ are shifted by $0.1\,\mathrm{J/mol\,K^2}$ with respect to each other.

For $x \geq 0.15$ all compounds feature one or more weak anomalies in c_p/T, which coincide with the anomalies in $\alpha(T)$. For $x = 0.15$ and 0.17 the LTM and the magnetic phase transition occur at similar temperatures. In the $\alpha(T)$ data of the higher doped specimens the onset of ferromagnetism is indicated by kinks. These kinks might be hidden by the large LTM anomalies for $x = 0.15$ and 0.17. Therefore one cannot distinguish if the anomalies in c_p/T for these two compounds are caused by the magnetic or a different transition. For $x = 0.19$ the specific-heat data features only a weak shoulder around the temperature of the corresponding LTM. The anomalies visible in the data of the higher doped compounds $x \geq 0.2$ are clearly related to the ferromagnetic phase transition. The structural phase transition shifts with increasing x to higher temperatures and causes in both quantities clear anomalies. The appearance of the HTM in $\alpha(T)$ ($\diamond$) and of the maxima at higher temperatures in c_p/T take place at similar temperatures. For $x = 0.2$ one can see a weak maximum in the specific-heat data above room temperature which agrees with the onset of a minimum in the thermal-expansion data. The origin of the LTM which is visible in $\alpha(T)$ is not clear yet. This anomaly vanishes for $x > 0.21$ and possibly does not affect the specific heat. The investigation of its origin is still under progress and will be reported elsewhere.

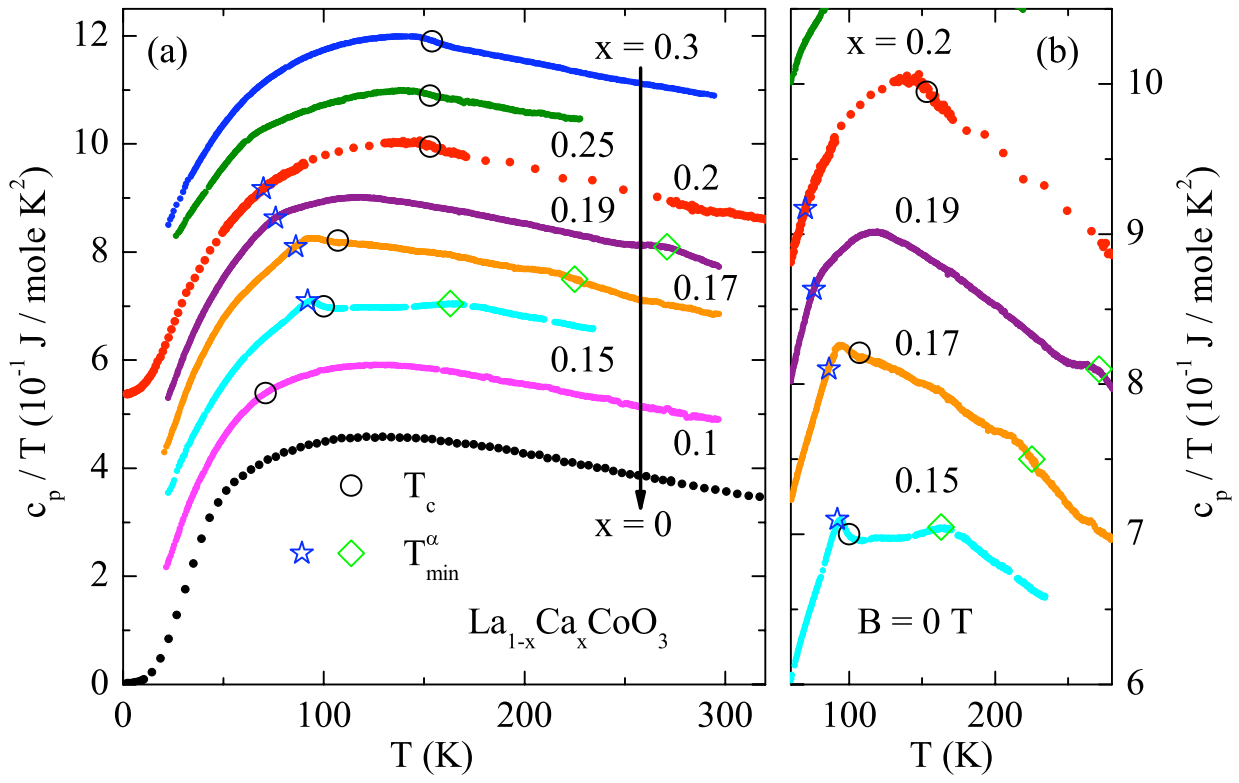

Fig. 3. Specific Heat c_p/T of $La_{1-x}Ca_xCoO_3$: $\star$ and $\diamond$ mark the occurrence of the LTM and HTM in $\alpha(T)$, ○ signals the ferromagnetic phase transition. Panel (b) shows an enlarged view of the intermediate doping region $0.15 \leq x \leq 0.2$. For clarity the different data sets are shifted by $0.1\,\mathrm{J/mol\,K^2}$ with respect to each other.

In summary, we have studied the influence of hole doping on the series $La_{1-x}Ca_xCoO_3$ by thermal-expansion and specific-heat measurements. Depending on the concentration x we observe up to three distinct anomalies. One of them is related to the ferromagnetic ordering, while a second one arises from a first-order structural phase transition. The origin of the third anomaly remains to be clarified.

3. Acknowledgments

This work was supported by the Deutsche Forschungsgemeinschaft through SFB 608.

References

[1] C. Zobel *et al.* Phys. Rev. B **66**, 020402 (2002).
[2] J. Baier *et al.* Phys. Rev. B **71**, 014443 (2005).
[3] M. Itoh *et al.* J. Phys. Soc. Japan **63**, 1486 (1994).
[4] M.A. Señarís-Rodríguez and J.B. Goodenough. J. of Solid State Chem. **116**, 224 (1995).
[5] M.A. Korotin *et al.* Phys. Rev. B **54**, 5309 (1996).
[6] M. Kriener *et al.* Phys. Rev. B **69**, 094417 (2004).